



*Institute of Paper Science and Technology
Atlanta, Georgia*

IPST Technical Paper Series Number 878

Influence of Carbohydrate Physical Factors During Pulping and Bleaching

D.R. Dimmel, H.J. Willenbrink, and P. Van Vreede

August 2000

Submitted to
Journal of Wood Chemistry and Technology

Copyright© 2000 by the Institute of Paper Science and Technology

For Members Only

INSTITUTE OF PAPER SCIENCE AND TECHNOLOGY PURPOSE AND MISSIONS

The Institute of Paper Science and Technology is an independent graduate school, research organization, and information center for science and technology mainly concerned with manufacture and uses of pulp, paper, paperboard, and other forest products and byproducts. Established in 1929 as the Institute of Paper Chemistry, the Institute provides research and information services to the wood, fiber, and allied industries in a unique partnership between education and business. The Institute is supported by 50 member companies. The purpose of the Institute is fulfilled through four missions, which are:

- to provide a multidisciplinary graduate education to students who advance the science and technology of the industry and who rise into leadership positions within the industry;
- to conduct and foster research that creates knowledge to satisfy the technological needs of the industry;
- to provide the information, expertise, and interactive learning that enables customers to improve job knowledge and business performance;
- to aggressively seek out technological opportunities and facilitate the transfer and implementation of those technologies in collaboration with industry partners.

ACCREDITATION

The Institute of Paper Science and Technology is accredited by the Commission on Colleges of the Southern Association of Colleges and Schools to award the Master of Science and Doctor of Philosophy degrees.

NOTICE AND DISCLAIMER

The Institute of Paper Science and Technology (IPST) has provided a high standard of professional service and has put forth its best efforts within the time and funds available for this project. The information and conclusions are advisory and are intended only for internal use by any company who may receive this report. Each company must decide for itself the best approach to solving any problems it may have and how, or whether, this reported information should be considered in its approach.

IPST does not recommend particular products, procedures, materials, or service. These are included only in the interest of completeness within a laboratory context and budgetary constraint. Actual products, materials, and services used may differ and are peculiar to the operations of each company.

In no event shall IPST or its employees and agents have any obligation or liability for damages including, but not limited to, consequential damages arising out of or in connection with any company's use of or inability to use the reported information. IPST provides no warranty or guaranty of results.

The Institute of Paper Science and Technology assures equal opportunity to all qualified persons without regard to race color, religion, sex, national origin, age, disability, marital status, or Vietnam era veterans status in the admission to, participation in, treatment of, or employment in the programs and activities which the Institute operates.

INFLUENCE OF CARBOHYDRATE PHYSICAL FACTORS DURING PULPING AND BLEACHING

D. R. Dimmel, H. J. Willenbrink, and P. Van Vreede
Institute of Paper Science and Technology
500 10th Street NW, Atlanta, Georgia 30318 (U.S.A.)

ABSTRACT

The viscosities of pulp, cotton linters, crystalline cellulose, and amorphous cellulose samples have been measured as a function of time during simulated soda and soda/AQ pulping, oxygen delignification, and hydrogen peroxide bleaching. Typical drops in viscosities for amorphous cellulose samples were 90%; while crystalline cellulose showed, under identical conditions, drops of ~40% during simulated pulping and 0-10% during simulated oxygen delignification and hydrogen peroxide bleaching. Anthraquinone did not cause significant chain cleavage in amorphous cellulose. The chemistry of amorphous cellulose appears to parallel that of pulp, in that metals that are harmful or protective during pulp delignification show the same trends with small-scale reactions of amorphous cellulose. However, amorphous cellulose greatly exaggerates the nature of the chemistry and thus appears to be an ideal substrate for studying carbohydrate chain cleavage reactions under different pulping and bleaching conditions. The low reactivity of pulp is probably related to its high crystalline cellulose content.

INTRODUCTION

The goal of chemical pulping and bleaching is to liberate, without degradation, carbohydrate fibers from wood while simultaneously removing the lignin. Unfortunately, current processes exhibit large carbohydrate losses, comparable to, or even exceeding, that of the lignin. Reduction of the carbohydrate chain length, leading to decreased pulp viscosity and product strength, also occurs. The research

reported here concerns searching for an appropriate substrate to study carbohydrate chain cleavage reactions and highlighting the importance of physical structure in such reactions.

The term carbohydrate "physical" structure refers to whether the carbohydrate is (a) soluble in the medium and free to rotate, ring flip, etc., (b) insoluble but able to flex (i.e., amorphous cellulose), or (c) insoluble and fixed in space (i.e., crystalline cellulose). The concept of physical structure having a bearing on carbohydrate chemistry was first introduced by Haas, Hrutfiord, and Sarkanen in 1967.¹ This group, together with Gentile et al.² in 1987, demonstrated that physical stopping is more important than chemical stopping in preventing losses of cellulose yield during alkaline treatments.

We have been interested in the chemistry of cellulose chain cleavage, having examined the influence of restricted ring flipping,³ insoluble cellulose models,⁴ and the chemistry of amorphous and crystalline cellulose in typical pulping and bleaching reactions.^{5,6} This report details the latter work and serves as an introduction for the ozone chemistry of amorphous and crystalline cellulose.⁷

RESULTS AND DISCUSSION

Sample Preparation and Analysis

Cotton linters are primarily crystalline cellulose with a small amount of the amorphous cellulose present. Pure crystalline cellulose was prepared by treating cotton linters with mild acid until the degree of polymerization (DP) leveled off (> 8 hr); the acid hydrolyzes the amorphous material.⁸ Amorphous cellulose was prepared by dissolving cotton linters in DMSO/Et₂NH/SO₂ and precipitating into methanol/water.⁹ The cellulose samples were then each reduced with sodium borohydride to prevent monomer "peeling" losses when heated in alkali. There was a drop in viscosity with each operation: linters at 60 cps viscosity → 33 cps crystalline cellulose and 45 cps amorphous cellulose.

Two procedures were used to estimate to the extent of carbohydrate chain cleavage reaction. One involved carbanilation of the carbohydrate hydroxyl groups with phenyl isocyanate, followed by determination of molecular weight distributions by gel phase chromatography (GPC).¹⁰ While much useful information can be obtained by GPC, the method is very time-consuming. The other procedure measures the viscosity of a specific concentration of cellulose in a solvent; it is fast but less informative with regard to molecular weight distributions. In our case, the two methods correlated well (Figure 1); consequently, the faster method was most often used.

Pulping-like Reactions

Each cellulose sample exhibited a viscosity loss upon heating in 1 M NaOH at 150-2°C (Figure 2 and 3). After 2 hours, the percent changes in viscosities were: crystalline cellulose - 50%, cotton linters - 70%, and amorphous cellulose - 90%. Most of the viscosity loss in the amorphous case occurred in the first 15 minutes; the slow drop after 15 minutes probably reflects the occurrence of crystallization. Gentile et al. report that amorphous cellulose converts to crystalline cellulose at 60-80°C in alkali.²

Anthraquinone (AQ) in alkali has been reported to cause oxidation of alcohol groups¹¹ and more rapid degradation of amylose¹² than comparable experiments done in the absence of AQ. In both cases, the AQ was interacting with a soluble substrate. Does such chemistry also occur with an insoluble carbohydrate? To answer this question, we briefly examined the interaction of AQ with amorphous cellulose. High levels of AQ were employed since the system is not set up to regenerate AQ, as is the case with the pulping of wood.¹³ The temperature and time of the treatments were also lowered in order to decrease the amount of degradation and provide greater differences; a direct comparison to cotton linters was also performed. The data are presented in Table 1.

TABLE 1.
Cellulose Viscosities (cps) after Heating in 1 M NaOH with/without AQ.^a

Linters, 148-50°C, 60 Min			Amorphous, 135-7°C, 10 Min		
Starting Viscosity	No AQ Viscosity	AQ Viscosity	Starting Viscosity	No AQ Viscosity	AQ Viscosity
64.0	27.5 (27.1-28.0) ^b	29.3 (28.2-30.5) ^b	34.8	16.2 (14.0-18.0) ^b	14.6 (13.9-15.5) ^b
67.2	35.8 (32.5-38.4) ^c	32.4 (31.3-33.4) ^c	51.9	24.9 (21.7-26.8) ^c	22.1 (18.0-24.1) ^c

^aAnthraquinone moles equivalent to the moles of glucose units in the cellulose.

^bRange for triplicate sample cooks to give the average listed above.

^cRange for six cooks to give the average listed above.

In 3 of the 4 samples, the cooks done in the presence of large levels of AQ had slightly bigger viscosity drops. Based on the limited data collected, we conclude that AQ causes few chain cleavage reactions for insoluble carbohydrate substrates. This was the expected result for two reactants that are completely insoluble in alkali at high temperatures.¹⁴ Our results do not rule out that AQ *species* cause chain cleavage reactions, since anthrahydroquinone radical anion, a soluble intermediate oxidation state of AQ present during pulping,¹³ may be a carbohydrate oxidizer. The decreased tear strengths often observed with soda/AQ pulping are likely attributed to the higher alkalinity of such cooks¹⁵⁻¹⁷ and to retention of hemicelluloses.^{18,19}

A mild alkaline degradation of amorphous cellulose, which was performed in the presence of 0, 25, 50, and 100 mg of NaCl, gave nearly the same viscosity values as a function of time. Thus, increasing the ionic strength (dead load) of the system appeared to have little effect on the extent of carbohydrate chain cleavage.

Oxygen/Alkali Reactions

The viscosities observed when heating amorphous cellulose at 100°C for different time periods in 0.1 M NaOH under selected conditions are given in Table 2 and Figure 4. In comparison to the nitrogen control, oxygen leads to a more rapid viscosity loss, especially in the presence of cobalt. The other metal tested, magnesium, had a stabilizing effect when used alone in the alkaline-oxygen system (Table 2). The amorphous cellulose degradation rate (viscosity loss) was not, however, completely retarded in both the oxygen and nitrogen control cases by the presence of magnesium. Surprisingly, the combination of magnesium and cobalt caused a greater loss in viscosity than when cobalt was used alone (Table 2).

TABLE 2.
Viscosities Changes Associated with Heating a 46-cps Amorphous Cellulose at 100°C in 1 M NaOH with/without Oxygen and Certain Metals

		Viscosities (cps) – Average (Duplicates)			
Gas	Metal	1 Hour	2 Hour	4 Hour	6 Hour
N ₂	--	41.5 (39.2, 43.7)	34.9 (34.6, 35.2)	29.9 (31.5, 28.2)	
O ₂	--	36.7 (38.2, 35.1)	31.1 (29.9, 32.2)	23.3 (23.7, 22.8)	
N ₂	1% Mg	39.5 (38.3, 40.6)	35.1 (35.2, 35.1)	31.7 (32.2, 31.1)	28.0 (29.3, 26.7)
O ₂	1% Mg	36.9 (36.3, 37.5)	38.5 (41.5, 35.5)	32.8 (32.9, 32.7)	26.2 (25.3, 27.0)
N ₂	0.308 μmole Co	35.6 (35.6, 35.7)	31.1 (29.4, 32.7)	21.7 (21.5, 22.0)	20.5 (21.5, 19.5)
O ₂	0.308 μmole Co	20.0 (18.9, 21.1)	6.2 (6.8, 5.5)	3.9 (4.2, 3.6)	3.2 (3.5, 2.9)
O ₂	1% Mg and 0.308 μmole Co	8.0 (7.5, 8.4)	4.0 (4.1, 3.9)	3.1 (2.9, 3.2)	

The two metals chosen for study, cobalt and magnesium, are known to cause chain cleavage reactions in the presence of oxygen in models¹⁸ and stabilized pulps,²¹⁻²² respectively. The results observed here parallel these known properties, but are unusual in a few aspects. The data indicate that the magnesium protecting effects are not lasting and apparently are not helpful in the presence of cobalt; the Mg-Co interaction was unexpected.²³ Also, cobalt promoted degradation in the nitrogen control case, possibly indicating that the control was not completely oxygen-free.

The response of the amorphous cellulose-oxygen-alkali system to different levels of cobalt is shown in Figure 5. The cobalt appears to have little effect below a level of 0.162 mole of CoSO_4 /100 g of amorphous cellulose. Above this level, there was a rapid drop in viscosity with increasing amounts of cobalt.

A comparison of the reactivities of cotton linters, kraft pulp, and amorphous and crystalline cellulose samples towards oxygen at 100°C in alkaline solutions that contained cobalt is shown in Figures 6 and 7. After four hours, the viscosity of the linters is roughly one-half that of the starting viscosity, while in the amorphous case it is one-tenth. The initial rapid drop in viscosity for the linters was likely due to the amorphous cellulose present in the sample. The viscosity losses for a cellulose sample towards oxygen-alkali-cobalt were slight.

As seen in the figures, there is a dramatic difference in reactivity between the crystalline and amorphous cellulose. The viscosity profiles for the amorphous cellulose and pulp samples in Figures 6 and 7 are not identical; the reasons for this are not clear. Two different amorphous cellulose samples were used to generate the data in the figures; possibly one of the samples still contains a small amount of crystalline material. Also, small differences in impurities between runs can have an impact on bleaching reactions that are very sensitive to metals.

The viscosity losses for a bleached kraft pulp under the oxygen-alkali-cobalt conditions were small. The data in Figure 6 show a straight-line response for the kraft pulp, with a slope similar to crystalline cellulose; the absolute values of the viscosity determinations were not, however, available in this case due to a

wrong, but consistent sample dilution. The data in Figure 7 show that the kraft pulp lost some viscosity initially and then became stable. Oxygen-alkali-cobalt treatment of a new unbleached kraft pulp produced no loss in viscosity over four hours. Obviously, kraft pulps are relatively stable to the conditions and must be fairly free of amorphous material, which is rapidly degraded.

Hydrogen Peroxide Reactions

Several hydrogen peroxide reactions were performed. The experiments were done at 50-60°C, 12% consistency, and initial pHs of 11; all reaction samples were still basic at the conclusion of the heating period. As expected, the viscosity drop of amorphous cellulose increased with increasing peroxide application (Table 3). Also, the addition of magnesium and silicate stabilized the amorphous cellulose towards extensive degradation. Copper also seemed to have a small stabilizing effect; however, this effect is probably related to copper-induced decomposition of the hydrogen peroxide, which would lower the level of the peroxide available for reaction.²⁴

TABLE 3.
Viscosities Values after Treating a 46-cps, 12% consistency
Amorphous Cellulose Sample with Different Levels of Hydrogen
Peroxide and Metal Salts at 60°C for 1 hr, and an Initial pH of 11.

Peroxide (%)	Alkali (%)	Additive	Viscosity (cps) Duplicates
--	0.033	--	44.5, 43.2
0.2	0.10	--	12.3, 10.7
0.4	0.15	--	7.1, 7.8
1.0	0.39	--	4.4, 4.5
0.4	0.14	0.37 M CuSO ₄	13.8, 10.1
0.4	0.13	0.2% MgSO ₄ and 4.5% Na ₂ SiO ₃	39.8, 35.1

A time study of the reaction of crystalline, amorphous, and cotton linters cellulose with 0.2% hydrogen peroxide at 50°C produced the data shown in Figure 8. The initial rapid 10% drop in viscosity in the crystalline case was not seen in a subsequent study with a new crystalline sample; here the viscosity showed no loss with time over a 0-40 min period. There is some uncertainty as to which set of data more accurately reflects the true response of crystalline cellulose towards peroxide; the data in Figure 8 imply that our first sample of crystalline cellulose may have had some amorphous cellulose present. Our data clearly show that, in the absence of stabilizers, hydrogen peroxide causes severe chain cleavage of amorphous cellulose and little, if any, cleavage of crystalline cellulose.

CONCLUSIONS

Our studies establish that there are large reactivity differences between crystalline and amorphous cellulose during simulated pulping and bleaching. The chemistry of amorphous cellulose appears to parallel that of pulp, in that metals that are harmful and protective during pulp bleaching²² show the same trends with small-scale reactions of amorphous cellulose. However, amorphous cellulose greatly exaggerates the nature of the chemistry and thus appears to be an ideal substrate for studying carbohydrate chain cleavage reactions under different pulping and bleaching conditions. The chemistry displayed by wood and pulp might simply be a result of reactions occurring with the amorphous regions in the pulp; it is apparent from our studies that crystalline cellulose is unreactive.

EXPERIMENTAL

Cellulose Samples

Amorphous cellulose was prepared from dried hydropulped cotton linters in 2.5-g quantities by a method described by Isogai.⁸ The linters were provided to us by Hercules, Inc.; initially we used grade ER4500 and later grade 351. Crystalline cellulose was obtained by treating the cotton linters for an extended period

with 0.25 N HCl. Ten-gram samples were soaked in 2.5 L of HCl for 2, 4, 8, and 24 hours at room temperature. The samples were washed with (4x500 mL) distilled water, or until acid-free, next washed with (2x125 mL) 5% NH₄OH and (5x500 mL) distilled water, and then freeze-dried. The sample viscosity had leveled out after eight hours. In general, a 24-hour treatment time was employed.

A sodium borohydride reduction step consisted of mixing a 10-g sample of cellulose with 1.5 L of 0.25 N NaBH₄ on a shaker for 2-3 days. The sample was washed with 2 L of 0.1 N NaOH and (6x1L) distilled water to a neutral pH and then freeze-dried.

The amorphous and crystalline and cellulose samples were analyzed by x-ray diffraction. Amorphous cellulose has a very broadband diffractogram, while crystalline cellulose has one large sharp signal separated from two closely spaced, semi sharp smaller signals.²⁵ The pulp used in our studies was a 38%-consistency unbleached loblolly pine pulp of kappa number 32.

Alkali Reactions at 150°C

Reaction mixtures were prepared under a nitrogen atmosphere in a glove bag with NaOH solutions using 30% ultra-pure NaOH in deionized, deoxygenated water in an attempt to minimize metals and oxygen in the solution. The cellulose samples and anthraquinone, where used, were weighed into small metal tube reactors inside a glove bag. The reactors, which were warmed and evacuated in a desiccator prior to use, were sealed before removal from the glove bag. The reactors were rotated in a constant-temperature oil bath over a specified period, generally at a temperature of 135-150°C. The temperature occasionally varied by ~2°C for what were intended to be identical cooks. The tubes were cooled and opened and the contents filtered and washed extensively with deionized water. Viscosities were determined on 40 mg of dry samples at 0.5% TAPPI standard T230.

Oxygen-Alkali Reactions

Numerous trials were conducted to determine the best way to conduct oxygen-alkali reactions on a small scale; the following procedure worked well for us. For this and other procedures described below we used sodium hydroxide solutions that were prepared with 30% ultra-pure NaOH in deionized water in an attempt to minimize metals in the solution. Approximately 2 L of 0.1 N NaOH solution was placed in a 4-L beaker and the level of the water marked on the beaker. As the water level dropped during the experiment, boiling water was added to keep the alkali level constant. For experiments with metal salts, we added specific concentrations of metals at this point. Oxygen was delivered through a gas dispersion tube that was fitted, by means of a rubber stopper, into the middle of a desiccator plate (a flat ceramic plate with numerous holes). The plate, which was placed near the bottom of the beaker, helped spread the gaseous bubbles throughout the solution. Cellulose samples (100 mg) were weighed into crucibles that had sinter-glass on one end and were open on the other end. The open end was covered with a 160x160-mesh polypropylene cloth that was stable at high temperature. The opening was secured by a strip of polypropylene.

The NaOH solution was brought to a boil and either oxygen or nitrogen was delivered through the dispersion tube, causing generous bubbling throughout the beaker. The crucibles containing the cellulose samples were pushed under the water level to begin the reaction. Crucibles were removed at specific time intervals, drained of their alkali solution, submerged briefly in distilled water to dilute the residual alkali, and the polypropylene cloth removed. The reacted cellulose was washed several times with distilled water, transferred to weighed vials, and freeze-dried. Dry weights were recorded and viscosities determined on 40-mg samples at 0.5% TAPPI standard T230. Select samples were also analyzed by GPC by a method described by Schroeder and Haigh.¹⁰

Peroxide Bleaching Reactions

Hydrogen peroxide solutions were prepared from a 31% stock solution and titrated to determine an accurate peroxide level. A combination of 0.05 and 0.001 N NaOH solutions were used to give a pH of 11.0 and a consistency of 12%. An alkaline peroxide solution (0.833 mL) was mashed into a 100-mg cellulose sample inside a vial. The vial was sealed with a screw cap and Teflon septa, placed in a lead-foil holder, and submerged in a 50°C oil bath. After a specific time period, the vial was removed and cooled. The sample was washed several times with distilled water, quantitatively transferred to a weighed vial, and freeze-dried. The dry weight was recorded and viscosities determined on 40-mg samples at 0.5% TAPPI standard T230.

ACKNOWLEDGEMENTS

We are grateful to Dr. Leland Schroeder for getting us started in this research and to Earl Malcolm for his counsel.

REFERENCES

1. D. W. Haas, B. N. Hrutfiord, and K. V. Sarkanen, *J. Appl. Polymer Sci.*, **11**, 587 (1967).
2. V. M. Gentile, L. R. Schroeder, and R. H. Atalla, *ACS Symp. Ser. no. 340*, Chap. 16, 272-291 (1987).
3. R. M. Kaylor, D. R. Dimmel, A. J. Ragauskas, and C. L. Liotta, *J. Wood Chem. Technol.*, **15**, 431 (1995).
4. M. J. Bovee, D. R. Dimmel, and L. R. Schroeder, *J. Wood Chem. Technol.*, **8**, 441 (1988).
5. D. R. Dimmel, H. Willenbrink, and E. W. Malcolm, Amer. Chem. Soc. Nat'l Mtg, Honolulu, December 20, 1989.
6. D. R. Dimmel, Proceed. 1994 Internat. Pulp Bleaching Conf., Vancouver, BC, Canada, June 13-16, 1994, Text of Posters, p. 107.
7. D. R. Dimmel et al., *J. Wood Chem. Technol.*, submitted.

8. T. Hattula, Paperi Puu, 69(2), 92 (1987) and references therein.
9. A. Isogai, A. Ishizu, and J. Nakano, Carbohydrate Research, 138, 99 (1985).
10. L. R. Schroeder and F. C. Haigh, Tappi, 62(10), 103 (1979).
11. A. F. A. Wallis and R. H. Wearne, J. Wood Chem. Technol., 7, 513 (1987); and references therein.
12. F. L. A. Arbin, L. R. Schroeder, N. S. Thompson, and E. W. Malcolm, Tappi, 63(4), 152 (1980); *ibid.*, Cellulose Chem. Technol., 15, 523 (1981).
13. D. R. Dimmel, J. Wood Chem. Technol., 5, 1 (1985).
14. C. Storgard-Envall and D. R. Dimmel, J. Wood Chem. Technol., 6, 367 (1986).
15. (a) P. J. Nelson and G. M. Irvine, Proceed. Internat. Symp. Wood & Pulping Chemistry, Raleigh, NC, May 22-25, 1989, p. 515; (b) P. J. Nelson and G. M. Irvine, Tappi J., 75(1), 163 (1992).
16. (a) C. R. Mitchell and J. H. Ross, Pulp and Paper Magazine of Canada, 33, p. 35 (March 1932); (b) J. H. Ross, U.S. Patent 1,922,262 (August 15, 1933); (c) S. D. Wells, U.S. Patent 1,949,669 (March 6, 1943).
17. A. Kettunen, J. E. Jiang, K. Harsia, and B. Marcoccia, Proceed. 1997 Tappi Pulping Conf., San Francisco, Oct. 20-23, 1997, p. 587.
18. R. P. Kibblewhite and A. D. Bawden, Appita, 42, 275 (1989).
19. A. Teder and D. Tormund, Tappi, 64(4), 138 (1981).
20. D. P. Graves, N. S. Thompson, and L. R. Schroeder, J. Wood Chem. Technol., 2, 115 (1982).
21. J. A. Histed, L. F. Sandel, Jr., and M. M. Hurst, in Pulp Bleaching: Principles and Practice, Editors C. W. Dence and D. W. Reeve, TAPPI Press, Atlanta, GA, 1996, p. 424-28.
22. I. Croon and D. H. Andrews, Tappi, 54(11), 1893 (1971).
23. A. F. Gilbert, E. Pavlovova, and W. H. Rapson, Tappi, 56(6), 95 (1973).
24. P. K. Smith and T. J. McDonough, Svensk Papperstid., 88(12), R106 (1985).
25. L. R. Schroeder, V. M. Gentile, and R. H. Atalla, J. Wood Chem. Technol., 6, 1 (1986).

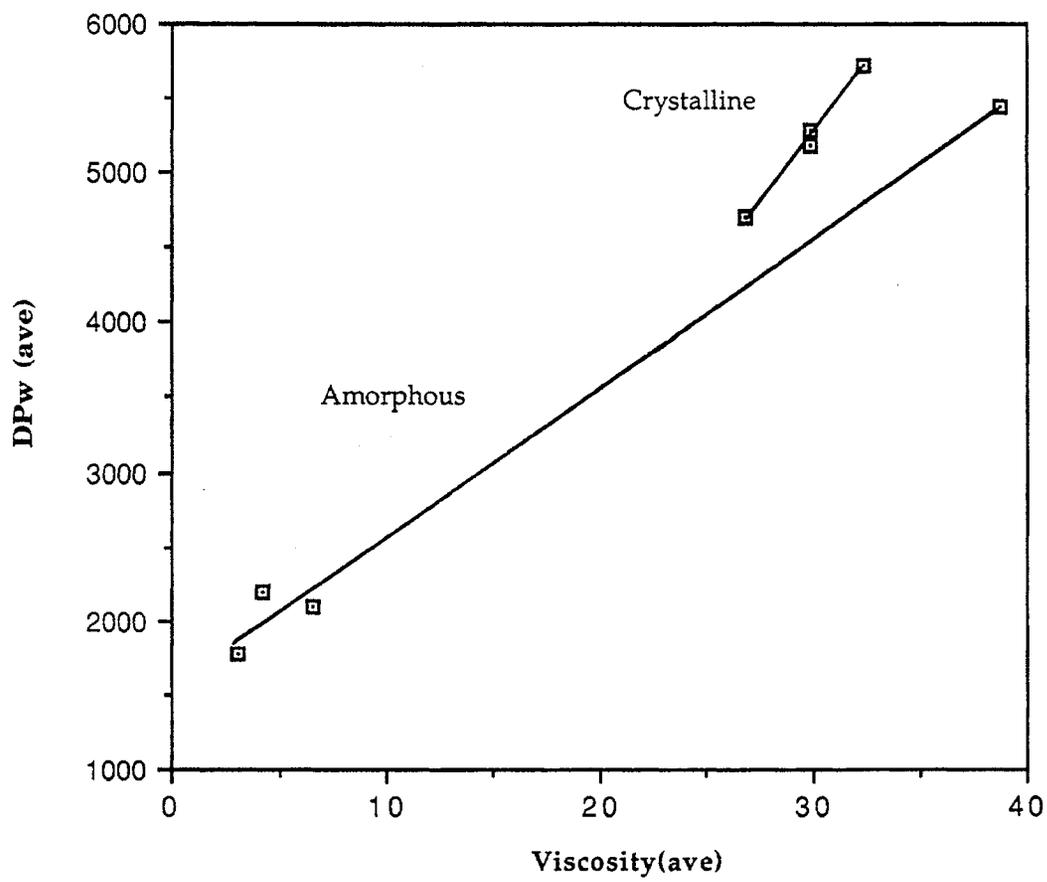


FIGURE 1. Correlation of DPW and viscosities (cps) for cellulose samples that were treated with oxygen/alkali/cobalt.

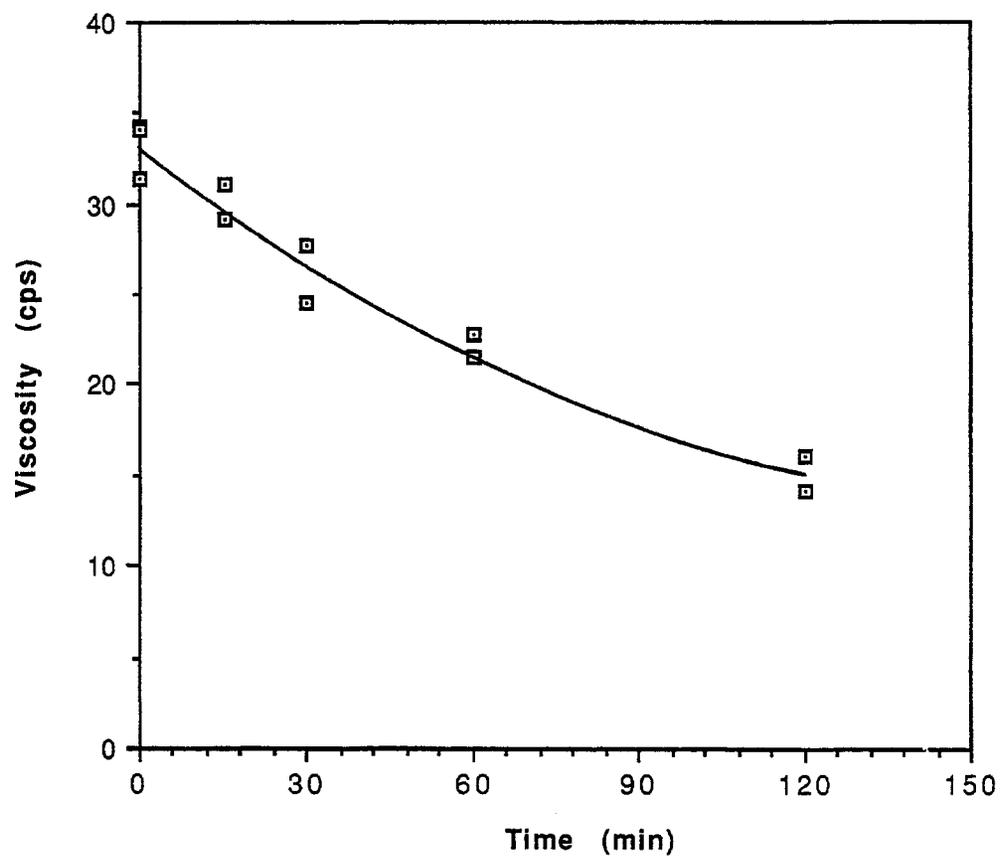


FIGURE 2. Viscosity changes as a function of time for heating crystalline cellulose at 150°C in 1 M NaOH.

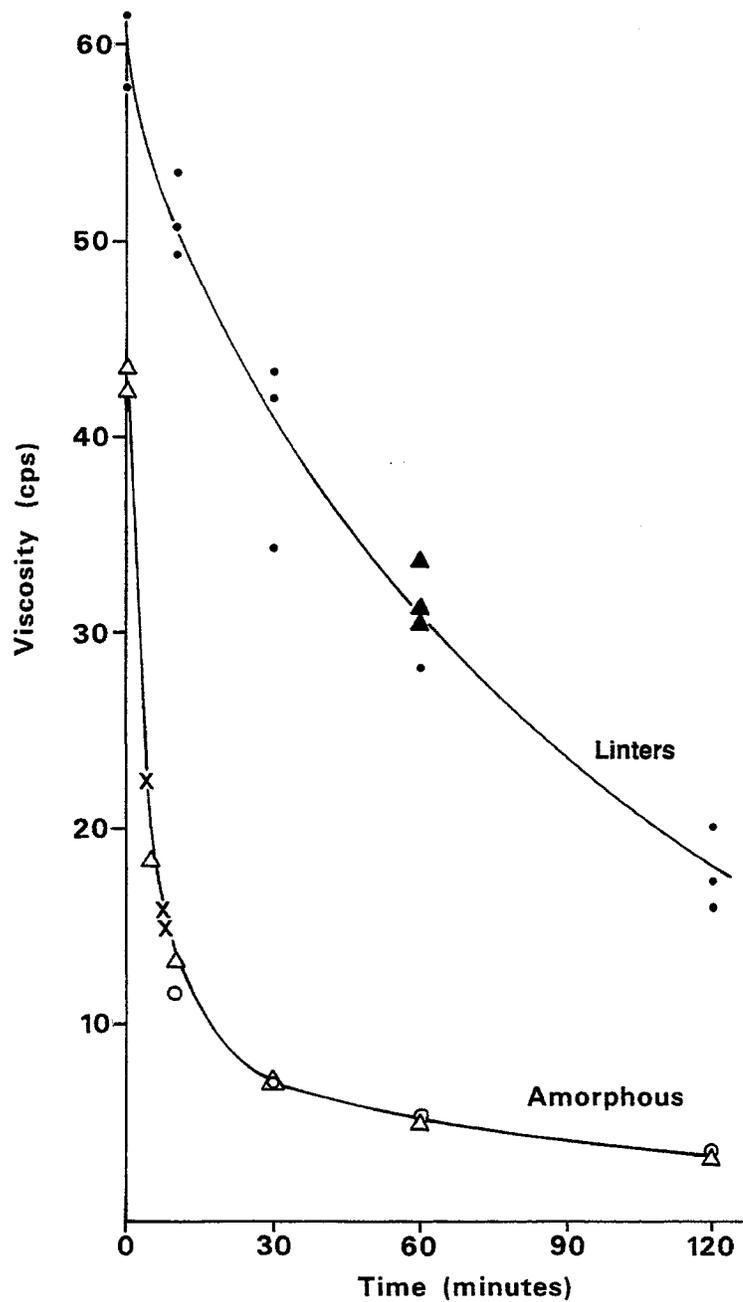


FIGURE 3. Viscosity changes as a function of time for heating cotton linters and amorphous cellulose at the 152°C in 1 M NaOH. The different symbols for each curve represent determinations done on different days.

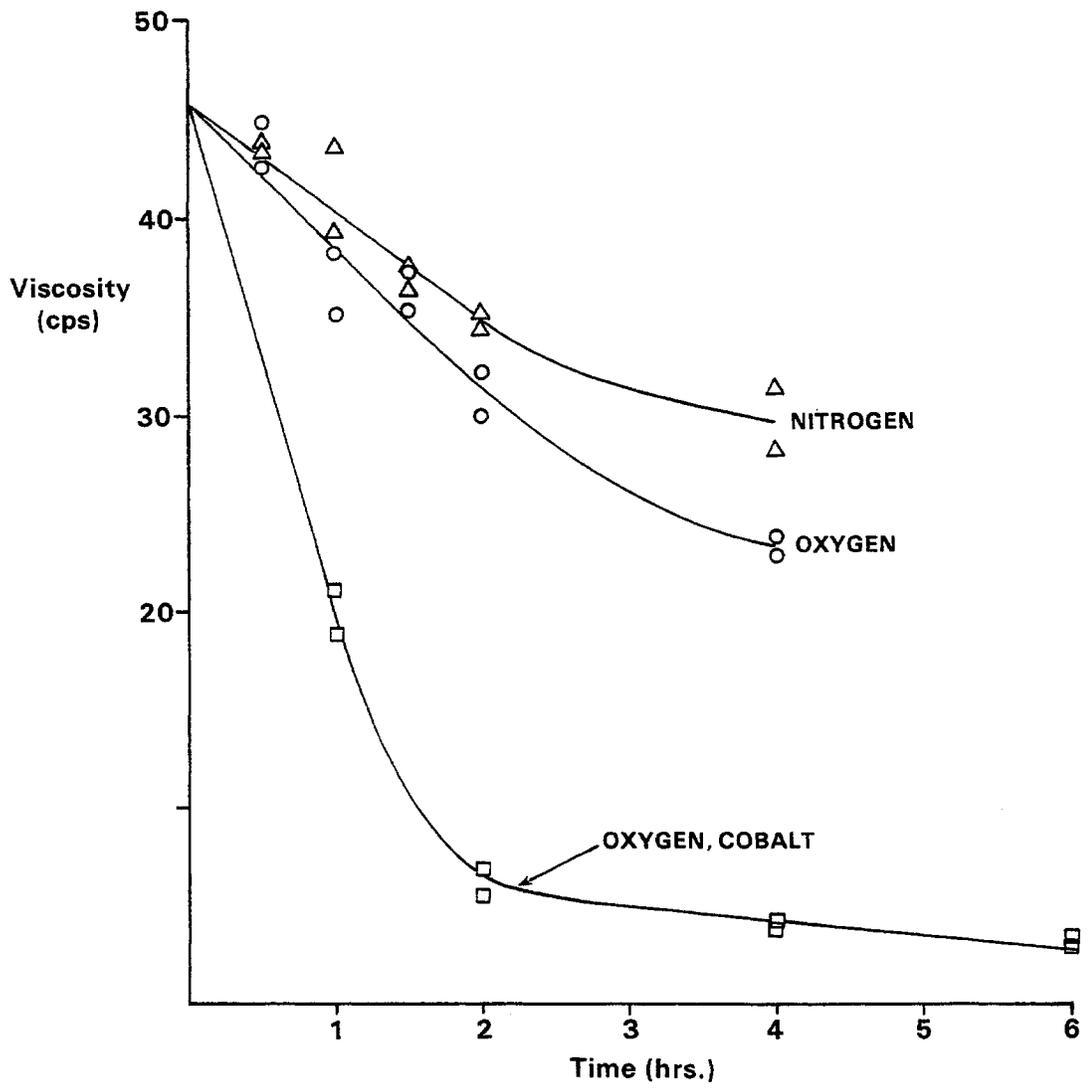


FIGURE 4. Viscosity variations as a function of time following duplicate treatments of amorphous cellulose at 100°C in 0.1 M NaOH with the indicated chemicals; cobalt sulfate was 0.308 mole/100 g sample.

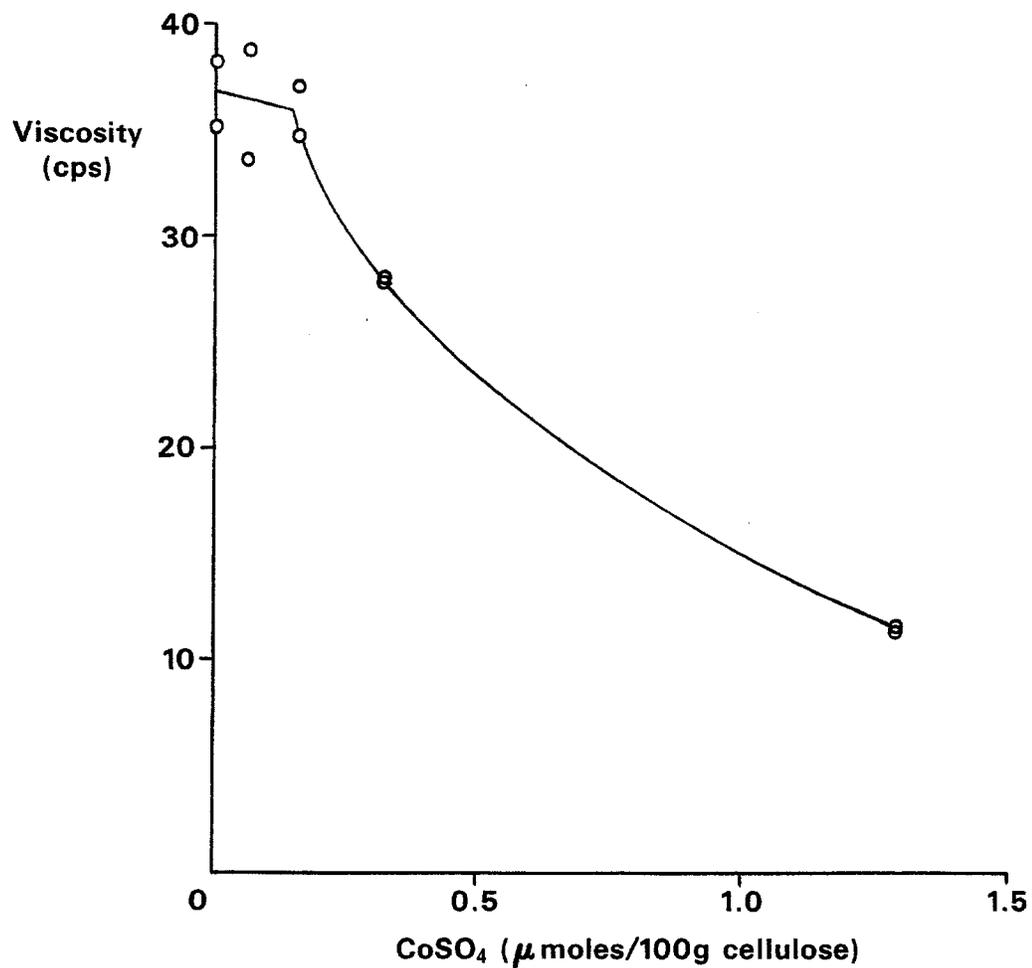


FIGURE 5. Variations in amorphous cellulose viscosities with different levels of cobalt for samples heated at 100°C for 1 hour in 0.1 M NaOH; duplicates were done at each cobalt level.

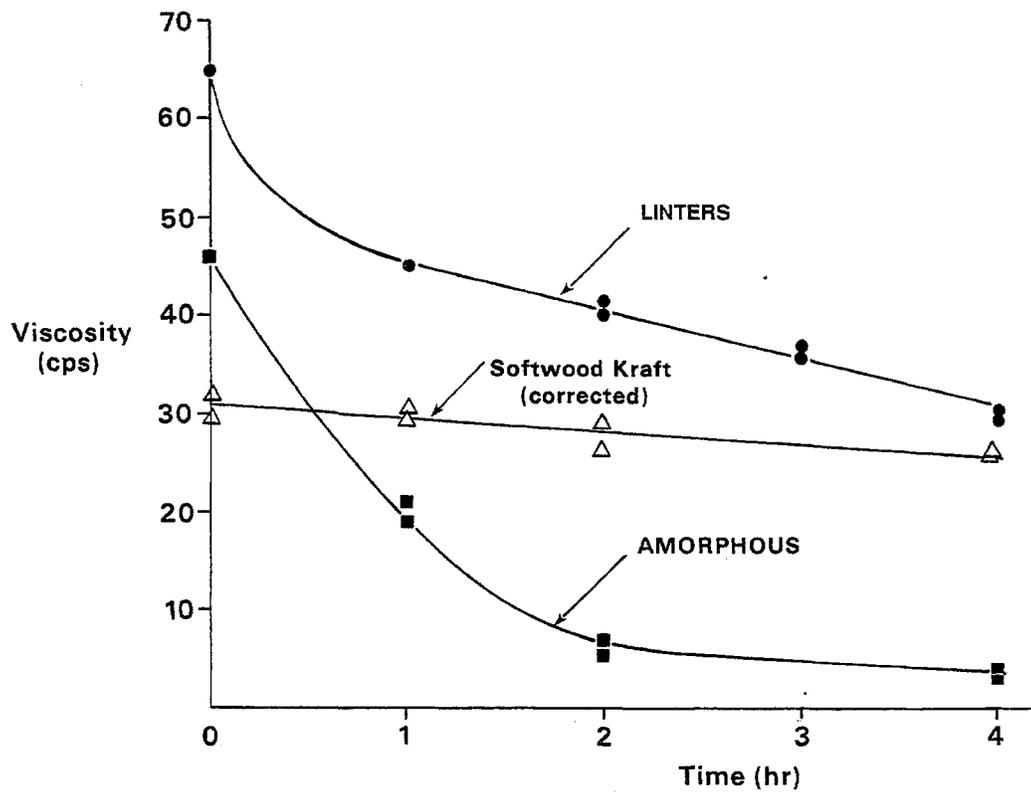


FIGURE 6. Viscosity variations as a function of time for treatment of different cellulose samples with oxygen, 0.1 M NaOH, 0.323 μ moles Co/100 mg sample at 100°C; duplicates were done in most cases.

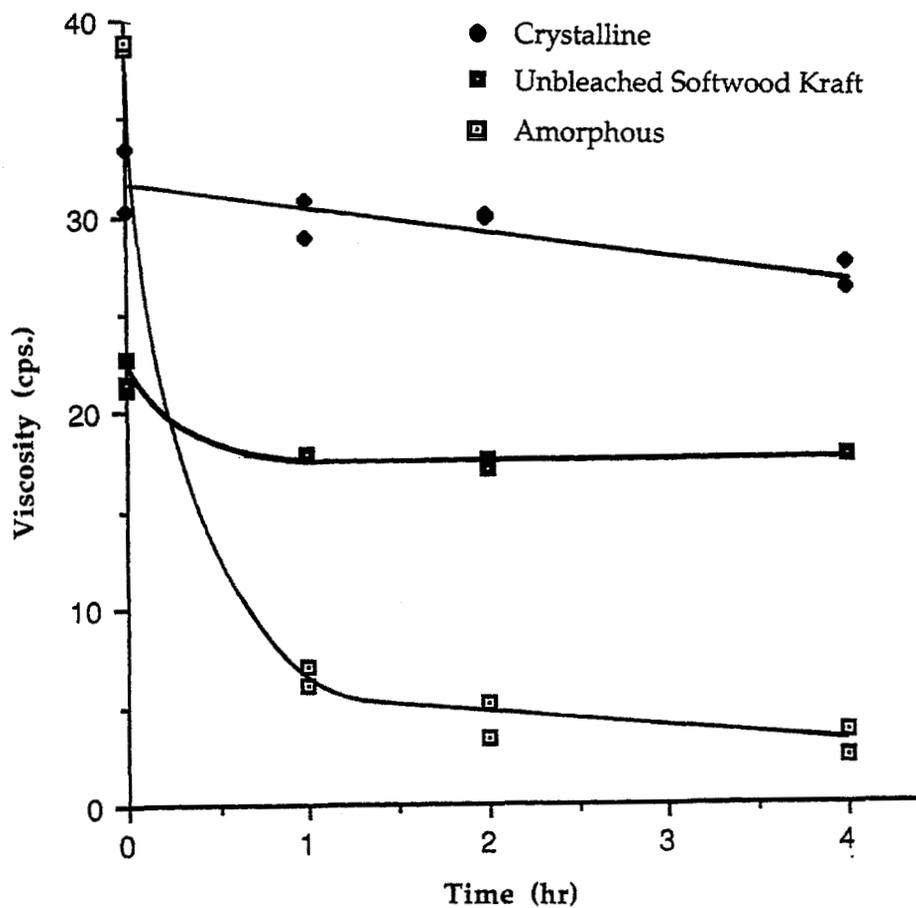


FIGURE 7. Viscosity variations as a function of time for treatment of different cellulose samples with oxygen, 0.1 M NaOH, 0.323 μ moles Co/100 mg sample at 100°C; duplicates were done in most cases.

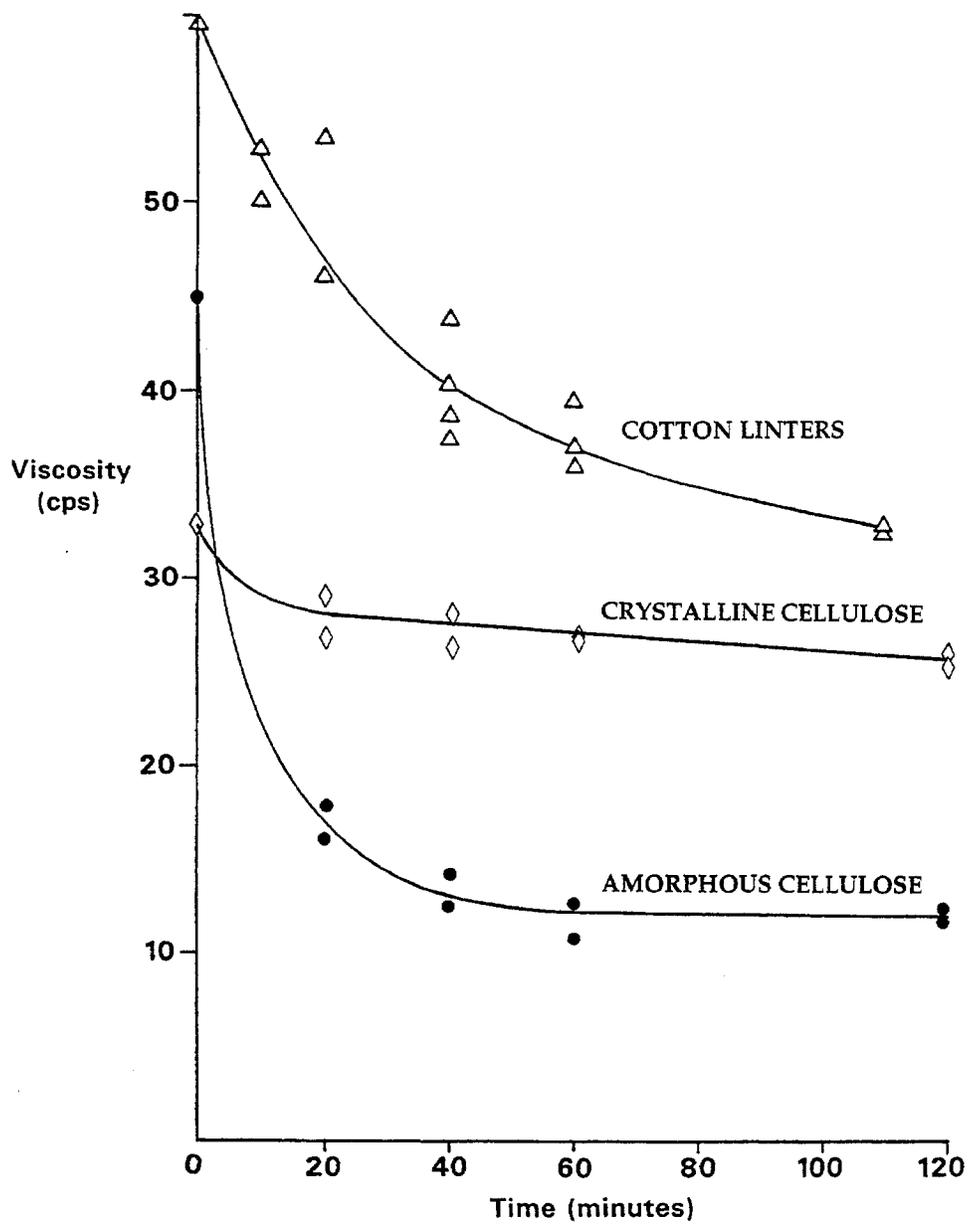


FIGURE 8. Viscosity variations as a function of time for the treatment of 12% consistency cellulose samples with 0.2% H₂O₂/0.10% alkali at 50°C.

